AD-A086 400 NAVAL SURFACE WEAPONS CENTER WHITE OAK LAB SILVER SP--ETC F/G 7/2
MAGNETOSTRICTION OF RARE EARTH-IRON COMPOUNDS RFE3 AND R6FE23,(U)
APR 80 R ABBUNDI, A E CLARK
UNCLASSIFIED NSWC/WOL/TR-78-88 NL

NSWC/WOL TR 78-88

MAGNETOSTRICTION OF RARE EARTH-IRON COMPOUNDS; RFe_3 AND R_6Fe_{23}

BY R. ABBUNDI A. E. CLARK

RESEARCH AND TECHNOLOGY DEPARTMENT

1 APRIL 1980

NAVAL SURFACE WEAPONS CENTER

Dahlgren, Virginia 22448 • Silver Spring, Maryland 20910

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE	READ INSTRUCTIONS BEFORE COMPLETING FORM
1 REPORT NUMBER: NSWC/WOL/TR-78-88	2 GOVT ACCESSION NO. / 3 RECIPIENT'S CATALOG NUMBER
4 TITLE (and Subtitle): Magnetostriction of Rare Earth-Iron Compounds; RFe_3 and R_6Fe_{23}	5 TYPE OF REPORT & PERIOD COVERED
	6 PERFORMING ORG. REPORT NUMBER
7 AUTHOR(s): R. Abbundi and A. E. Clark	8 CONTRACT OR GRANT NUMBER(s)
9 PERFORMING ORGANIZATION NAME AND ADDRESS: Naval Surface Weapons Center, White Oak, Silver Spring, MD 20910	10 PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS: 61153N; RR 02-206; RR 02-206-01; [illegible]
11 CONTROLLING OFFICE NAME AND ADDRESS	12 REPORT DATE: 1 April 1980
	13 NUMBER OF PAGES: 34
14 MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	15 SECURITY CLASS. (of this report): UNCLASSIFIED
	15a DECLASSIFICATION/DOWNGRADING SCHEDULE

16 DISTRIBUTION STATEMENT (of this Report)

Approved for public release; distribution unlimited.

17 DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)

18 SUPPLEMENTARY NOTES

A portion of this work to be published in the Journal of Magnetism and Magnetic Materials.

19 KEY WORDS (Continue on reverse side if necessary and identify by block number)

Rare Earth Intermetallic Compounds
Magnetostriction

20 ABSTRACT (Continue on reverse side if necessary and identify by block number)

The magnetostriction of the RFe_3 and R_6Fe_{23} compounds was measured from room temperature to 80 K (R = Sm, Tb, Dy, Ho, Er and Tm). In the rhombohedral RFe_3 series, $TbFe_3$ possesses the largest magnetostrictive strain with $\lambda_{\parallel} - \lambda_{\perp} = 990 \times 10^{-6}$ at room temperature and 1725×10^{-6} at 80 K. $SmFe_3$, although potentially a highly magnetostrictive compound, possesses a strain of only -316 ppm at room temperature due to the fact that the easy axis of magnetization is along the c-axis. The temperature

DD FORM 1 JAN 73 1473 EDITION OF 1 NOV 65 IS OBSOLETE
S/N 0102-LF-014-6601

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

391516

dependence of the magnetostriction of $TmFe_3$ is complex. In the cubic R_6Fe_{23} series the magneto-strains of Er_6Fe_{23} and Tm_6Fe_{23} increase substantially with decreasing temperature, due to the rapid ordering of the rare earth sublattice. The strain in Er_6Fe_{23} increases nearly 7-fold from -57 ppm at 300 K to -392 ppm at 80 K. Tm_6Fe_{23} shows a nearly 10-fold increase from -37×10^{-6} to -362×10^{-6}. The signs of the magnetostriction for both the RFe_3 and R_6Fe_{23} series are consistent with those predicted by the Stevens' factor.

FOREWORD

The magnetostriction study reported here is part of a research program undertaken to determine the nature of the magnetostriction in the rare earth-iron intermetallic compounds. In this report is detailed the temperature dependence of the magnetostriction for a series of RFe_3 and R_6Fe_{23} compounds. Studies were made as a function of applied field at various temperatures from room temperature to 80 K.

In the RFe_3 series $TbFe_3$ possesses the largest magnetostrictive strain with $\lambda_{\parallel} - \lambda_{\perp} = 990 \times 10^{-6}$ at room temperature and 1725×10^{-6} at 80 K. $SmFe_3$, although potentially a highly magnetostrictive compound possesses a strain of only -316 ppm at room temperature due to the fact that the easy axis of magnetization is along the c-axis.

In the R_6Fe_{23} series the magneto-strains of Er_6Fe_{23} and Tm_6Fe_{23} increase substantially with decreasing temperature, due to the rapid ordering of the rare earth sublattice. The strain in Er_6Fe_{23} increases nearly 7-fold from -57 ppm at 300 K to -392 ppm at 80 K. Tm_6Fe_{23} shows a nearly 10-fold increase from -37×10^{-6} to -362×10^{-6}.

The study was carried out in the Solid State Branch of the Radiation Division as part of the research program on magnetostrictive materials. The research was sponsored by the Office of Naval Research (PO-4-0081, NR 039-110) and the NSWC Independent Research Program (IR-011).

B. F. DESAVAGE
By direction

CONTENTS

ILLUSTRATIONS

TABLES

INTRODUCTION

Previous work on the cubic Laves phase rare earth-Fe_2 compounds has shown that these materials possess enormous magnetostriction constants. In some of these compounds this huge strain is even present at room temperature. Both $TbFe_2$ and $SmFe_2$ possess a room temperature magnetostriction $|\lambda| > 2000$ ppm.[1]

Although the magnetostriction of the RFe_2 compounds (R = Sm, Tb, Dy, Ho, Er and Tm) has been extensively studied,[1-4] little attention has been paid to the magnetostriction of the remaining rare earth-iron intermetallic compounds. Here we report measurements of the magnetostriction of the RFe_3 and R_6Fe_{23} compounds from room temperature to 80K. The room temperature magnetostrictions of the R_2Fe_{17} compounds were also investigated.

In the rare earth-iron series the Curie temperatures are the highest for the RFe_2 compounds (560-710K)[5,6] and decrease with increasing iron concentration. Just the opposite is true for the rare earth-cobalt and rare earth-nickel series.[7,8]

Mössbauer effect measurements[9-13] have been reported on the RFe_3 series at various temperatures. These results indicate the direction of the magnetization in these compounds. An attempt will be made to correlate the direction of the magnetization with the behavior of the magnetostriction as a function of temperature.

EXPERIMENTAL RESULTS

For all R, the magnitude of the magnetostriction at room temperature in the RFe_3 and R_6Fe_{23} compounds is smaller than that in the RFe_2 compounds.[1] However, as shown in Table I, the trend reverses with an increase in the magnitude of the magnetostriction as the concentration of rare earth decreases from R_6Fe_{23} to R_2Fe_{17}.

TABLE I. Room temperature magnetostriction $(\lambda_{\parallel} - \lambda_{\perp}) \times 10^{-6}$ at 25 kOe.

R	RFe_2[a]	RFe_3	R_6Fe_{23}	R_2Fe_{17}
Sm	-2340	-316	††	-95
Tb	2630	991	**	-21
Dy	650	514	**	-90
Ho	120	85	88	-159
Er	-449	-103	-57	-83
Tm	-185	-66	-37	-45

a) Compiled by A. Clark. Handbook on the Physics and Chemistry of Rare Earths, Ed. K. Gschneider and L. Eyring, North Holland Publishing Co. (1979), Volume II.

†† The compound Sm_6Fe_{23} does not form.

** Attempts to prepare single phase Tb_6Fe_{23} and Dy_6Fe_{23} were unsuccessful.

Figures 1-3 show the room temperature magnetostriction as a function of applied field for the RFe_3, R_6Fe_{23} and R_2Fe_{17} series. Unexpected results were obtained for the R_2Fe_{17} compounds, where the sign of the magnetostriction for all the compounds was negative. The only exception was Tb_2Fe_{17} in the as-cast (unannealed) state, where $\lambda_{\parallel} - \lambda_{\perp} = 197 \times 10^{-6}$ at H = 25 kOe. This is in contrast to the results on a Tb_2Fe_{17} sample after annealing which yields $\lambda_{\parallel} - \lambda_{\perp} = -21 \times 10^{-6}$ at 25 kOe. However examination of the field dependence in Figure 3 of the annealed specimen does

give some indication that there could possibly be a change in sign for this sample at larger fields. The R_2Fe_{17} compounds crystallize into a hexagonal Th_2Ni_{17}-type structure for R = Dy, Ho, Er and Tm. However, Strnat et al.[14] have reported that the x-ray pattern of Tb_2Fe_{17} displays lines belonging to this hexagonal structure as well as a rhombohedral Th_2Zn_{17}-type structure, with the hexagonal form being the high temperature modification. This possibly accounts for the difference in the magnetostriction observed for Tb_2Fe_{17} in the annealed and unannealed state.

A. RFe_3 COMPOUNDS

The RFe_3 compounds crystallize into a rhombohedral $PuNi_3$-type structure. Figure 4 shows the field dependence of the magnetostriction at various temperatures for $TbFe_3$. This compound possesses the largest magnetostrictive strain in the RFe_3 series with a room temperature $\lambda_{\parallel} - \lambda_{\perp} = 990 \times 10^{-6}$ at H = 25 kOe. Although the basal plane is easy throughout the entire temperature range with the magnetization along a b-axis,[9,10,12] the lack of saturation in the field dependence is indicative of the large magnetocrystalline anisotropy found in the Tb-Fe intermetallics.[15] Figure 8 shows the temperature dependence of the magnetostriction at H = 15 and 25 kOe. The strain in $TbFe_3$ increases monotonically with decreasing temperature reaching 1725×10^{-6} at 80 K.

The magnetostriction as a function of applied field for $SmFe_3$ at various temperatures is shown in Figure 5. While highly magnetostrictive at the lower temperatures, $\lambda_{\parallel} - \lambda_{\perp} = -1192 \times 10^{-6}$ at 80 K, $SmFe_3$ possesses only a moderate strain of -316 ppm at 300 K, resulting from the hard basal plane (c-axis easy) in this compound.[9] Although there has not been any determination of the easy axis in $SmFe_3$ below room temperature, the curves in Figure 5 do show a substantially larger strain at low fields below T = 150 K. The low temperature data also displays a "knee" in the curves which is totally absent near room temperature. The temperature dependence of the strain of $SmFe_3$ at H = 15 and 25 kOe is shown in Figure 8. $SmFe_3$ possesses the largest negative magnetostriction in the RFe_3 series.

Mössbauer effect measurements on $DyFe_3$ show that the magnetization rotates out of the basal plane toward the c-axis with decreasing temperature, making an angle of $\approx 26°$ with the basal plane at T = 77 K.[9-11] This accounts for the behavior of the magnetostriction displayed in Figure 8. The room temperature strain at H = 25 kOe was found to be 540×10^{-6} with a peak in the magnetostriction of 565 ppm occurring at T = 270 K. The rotation of the moment out of the basal plane results

in a decrease in λ below this temperature. Near 100 K the magnetostriction reaches a minimum of 265 ppm and then begins to increase in value with further temperature reduction as rotation of the moment ceases. The strain vs. field curves in Figure 6 for $DyFe_3$ saturate fairly well at room temperature but as the temperature is reduced the curves become "harder" as the moment pulls up out of the basal plane. At the lowest temperature measured T = 65 K the magnetostriction once again saturates, giving further evidence that the moment has ceased its rotation.

A change in the easy axis of magnetization has also been observed in $HoFe_3$. In this compound the Mössbauer effect reveals that near 100 K a spin reorientation occurs, with the magnetization moving from a b-axis to an a-axis as the temperature is lowered.[9,10] Figure 7 shows the magnetostriction as a function of applied field for $HoFe_3$ at various temperatures. The temperature dependence of the magnetostriction at H = 15 and 25 kOe is shown in Figure 8. The magnetostriction of $HoFe_3$ remains small over the entire temperature range in spite of the fact that the magnetization remains in the basal plane. At room temperature we find $\lambda_{\parallel} - \lambda_{\perp} = 85 \times 10^{-6}$ at 25 kOe. Below T = 225 K the strain vs. field curves become magnetically "harder", while in the temperature region 175 K > T > 125 K the high field magnetostriction is temperature independent. This behavior is presumably a result of the intermediate direction of the magnetization at these temperatures. Saturation, as well as an increase in λ, again occurs at temperatures below 100 K, with $\lambda_{\parallel} - \lambda_{\perp} = 183 \times 10^{-6}$ at T = 80 K.

The magnitude of the strain in $ErFe_3$ was found to undergo the largest change of any of the RFe_3 compounds. Figure 11 shows that the magnetostriction at H = 25 kOe increases nearly 6-fold from -103 ppm at 300 K to -595 ppm at 80 K. $ErFe_3$ possesses a compensation point in its magnetic moment at T = 239 K. This is reflected in the sharp "dip" in the magnetostriction at this temperature with an accompanying change in sign. The RFe_3 compounds previously discussed (with the exception of $SmFe_3$) also possess compensation points but they all occur above room temperature. The magnetostriction as a function of applied field for $ErFe_3$ at various temperatures is shown in Figure 9. Below the compensation temperature the curves do not saturate with the available fields. Neutron diffraction measurements[16] have determined that for T > 50 K a complex noncollinear magnetic structure occurs in $ErFe_3$. The moments on the two inequivalent Er sites, rather than being parallel, are oriented toward the c-axis and the basal plane respectively. All Fe moments are considered to be equal and parallel and are located ≈ 56° from the c-axis.

The temperature dependence of the magnetostriction of $TmFe_3$ is complex, as seen in Figure 11. The room temperature strain of -65 ppm is the smallest of the RFe_3 series. Below 300 K the magnitude of the magnetostriction begins increasing as the temperature is lowered, reaching a maximum negative strain of -325×10^{-6} at 175 K. At this point the magnetostriction decreases in magnitude with further temperature reduction until T = 100 K, where λ was found to remain constant with temperature until a compensation point at 78 K causes a sign reversal. Following this, the magnitude of the strain increases rapidly with temperature reaching -179×10^{-6} at 59 K, the lowest temperature measured. Figure 10 shows the field dependence of the magnetostriction at various temperatures for $TmFe_3$. Below 175 K the strain vs. field curves become increasingly harder to saturate with $|\lambda|$ decreasing with temperature for all field values. At the lowest temperature measured T = 59 K, Figure 10 shows that a large spontaneous magneto-strain of -100 ppm appears at 1 kOe, increasing to -179 ppm at 25 kOe as the magnetization rotates against a large anisotropy. In an effort to further investigate this behavior magnetic moment measurements from 4 - 300 K were performed on $TmFe_3$. The findings from this experiment closely parallel the results from the magnetostriction. Figure 12 shows the magnetization as a function of applied field at T = 300, 188 and 4.2 K. The moment curves depart from saturation at approximately 190 K and are extremely "hard" by 4.2 K. The temperature dependence of the magnetization at H = 5, 10 and 16 kOe is shown in Figure 13. The moment was found to decrease with temperature, even at 16 kOe, with the largest slope occurring in the region 200 K > T > 125 K. Coupling these results with the magnetostriction data, we infer that the easy axis of $TmFe_3$ is in the basal plane at high temperature with a rotation occurring between 100 K and 175 K, leaving the magnetization either along or close to the c-axis.

B. R_6Fe_{23} COMPOUNDS

The R_6Fe_{23} compounds crystallize into a cubic Th_6Mn_{23}-type structure. The magnetostriction of these compounds was found to be well behaved.

The strain in Ho_6Fe_{23} is rather small as in the RFe_3 and RFe_2 compounds. Figure 14 shows the field dependence of the magnetostriction at various temperatures while Figure 17 displays the temperature dependence at H = 25 kOe. At room temperature $\lambda_{\parallel} - \lambda_{\perp} = 88 \times 10^{-6}$ and increases only to 269×10^{-6} at 80 K. A compensation point is observed at 193 K.

The magnetostriction of Er_6Fe_{23} and Tm_6Fe_{23} increases substantially with decreasing temperature due to the rapid ordering of the rare earth sublattice in these two compounds. Figure 17 shows that the magnetostriction of Er_6Fe_{23} at 25 kOe increases nearly 7-fold from -57×10^{-6} at room temperature to -392×10^{-6} at 80 K. A compensation point was found at T = 100 K. Figure 15 shows the magnetostriction of this compound as a function of applied field for various temperatures. The magnetostriction is well behaved with an increasing anisotropy occurring at the lower temperatures.

Tm_6Fe_{23} undergoes the largest change of any of the R_6Fe_{23} compounds (see Figure 17) increasing nearly 10-fold from -37 ppm at 300 K to -362 ppm at 80 K and reaching -588 ppm at T = 55 K, the lowest temperature measured. Tm_6Fe_{23} is expected to have a compensation point below 40 K. Figure 16 shows that the field dependence of the magnetostriction saturates fairly well at all temperatures.

The magnetostrictions of Tb_6Fe_{23} and Dy_6Fe_{23} are not reported on since attempts to prepare single phase compounds were unsuccessful.

The signs of the magnetostriction for the R_6Fe_{23} compounds, as well as all compounds of the RFe_3 series, are consistent with those predicted by the Stevens' factor, α.[17]

REFERENCES

1. A. E. Clark, AIP Conf. Proc. 18, 1015 (1974).
2. A. E. Clark, R. Abbundi, H. T. Savage, and O. D. McMasters, Physica 86-88B, 73 (1977).
3. R. Abbundi and A. E. Clark, J. Appl. Phys. 49, 1969 (1978).
4. R. Abbundi, A. E. Clark, and N. C. Koon, J. Appl. Phys. 50, 1671 (1979).
5. K. H. J. Buschow and R. P. VanStapele, J. de Physique 32, C1-672 (1971).
6. A. E. Clark, R. Abbundi, and W. R. Gillmor, IEEE Trans. on Magnetics Mag-14, 542 (1978).
7. K. N. R. Taylor, Advances in Phys. 20, 551 (1971).
8. K. H. J. Buschow, Rep. Prog. Phys. 40, 1179 (1977).
9. A. M. van der Kraan, J. N. J. van der Velden, J. H. F. van Apeldoorn, P. C. M. Gubbens, and K. H. J. Buschow, Phys. Stat. Sol. 35A, 137 (1976).
10. S. K. Arif, D. St. P. Bunbury, G. J. Bowden, and R. K. Day, J. Phys. F 5, 1048 (1975).
11. S. Japa, K. Krop, R. Radwanski, and J. Wolinski, J. de Physique 40, C2-195 (1979).
12. S. K. Arif, D. St. P. Bunbury, and G. J. Bowden, J. Phys. F 5, 1785 (1975).
13. A. M. van der Kraan, P. C. M. Gubbens, and K. H. J. Buschow, Phys. Stat. Sol. 31A, 495 (1975).
14. K. Strnat, G. Hoffer, and A. E. Ray, IEEE Trans. on Magnetics Mag-2, 489 (1966).
15. A. E. Clark, J. R. Cullen, and K. Sato, AIP Conf. Proc. 24, 670 (1974).
16. R. L. Davis, R. K. Day, and J. B. Dunlop, J. Phys. F 7, 1885 (1977).
17. K. W. H. Stevens, Phys. Soc. 65, 209 (1952).

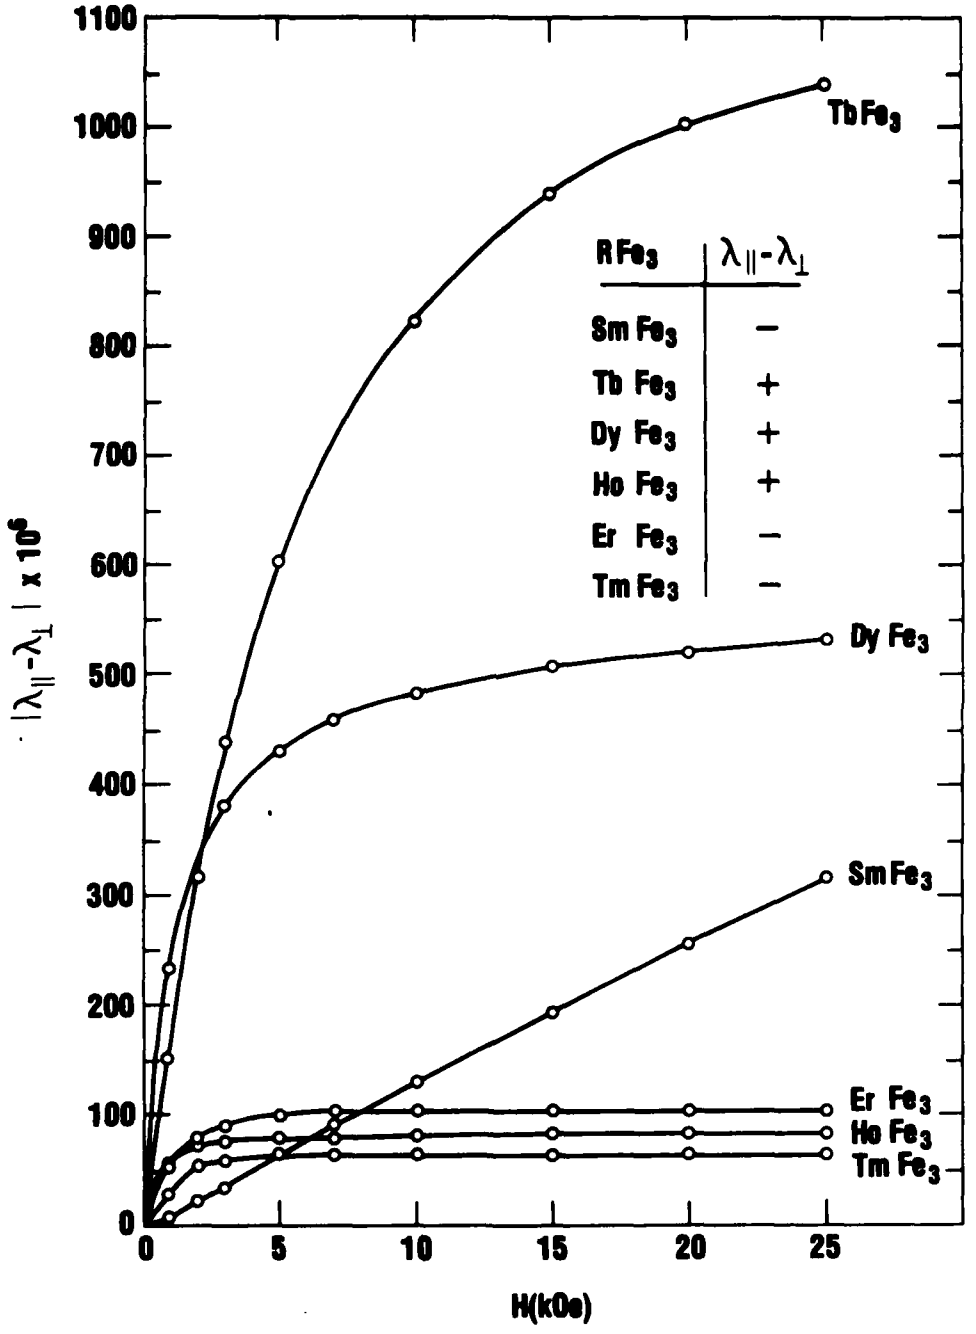

FIGURE 1 ROOM TEMPERATURE MAGNETOSTRICTION AS A FUNCTION OF APPLIED FIELD FOR VARIOUS RFe_3 COMPOUNDS

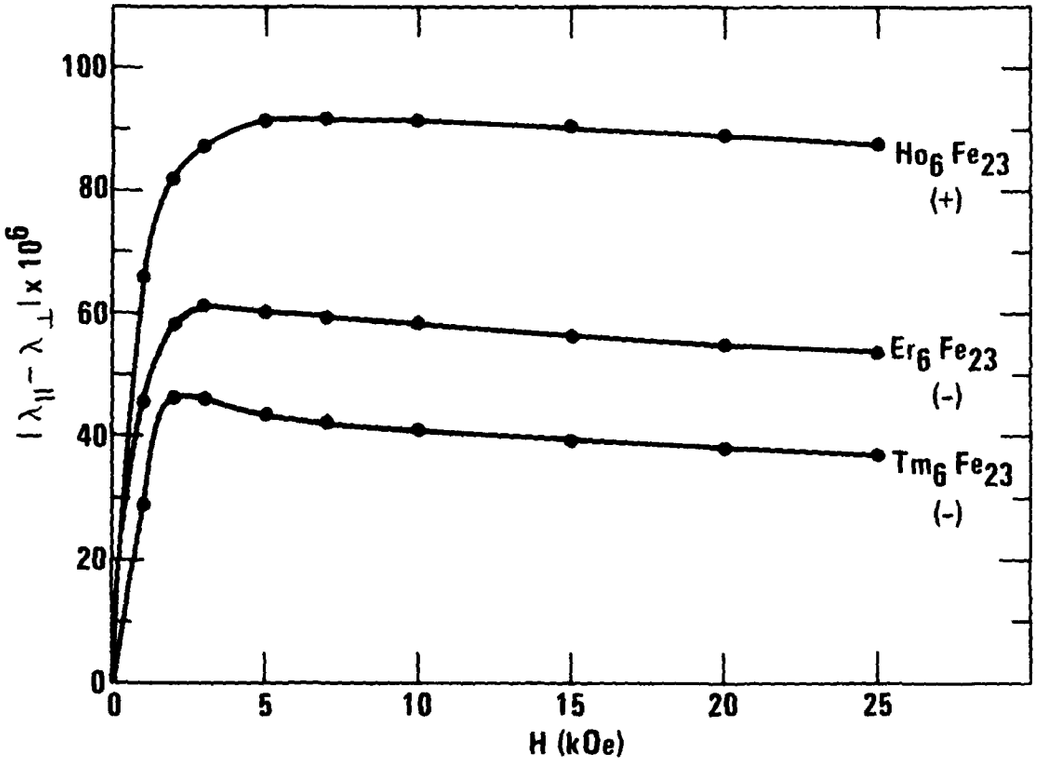

FIGURE 2 ROOM TEMPERATURE MAGNETOSTRICTION AS A FUNCTION OF APPLIED FIELD FOR VARIOUS $R_6 Fe_{23}$ COMPOUNDS

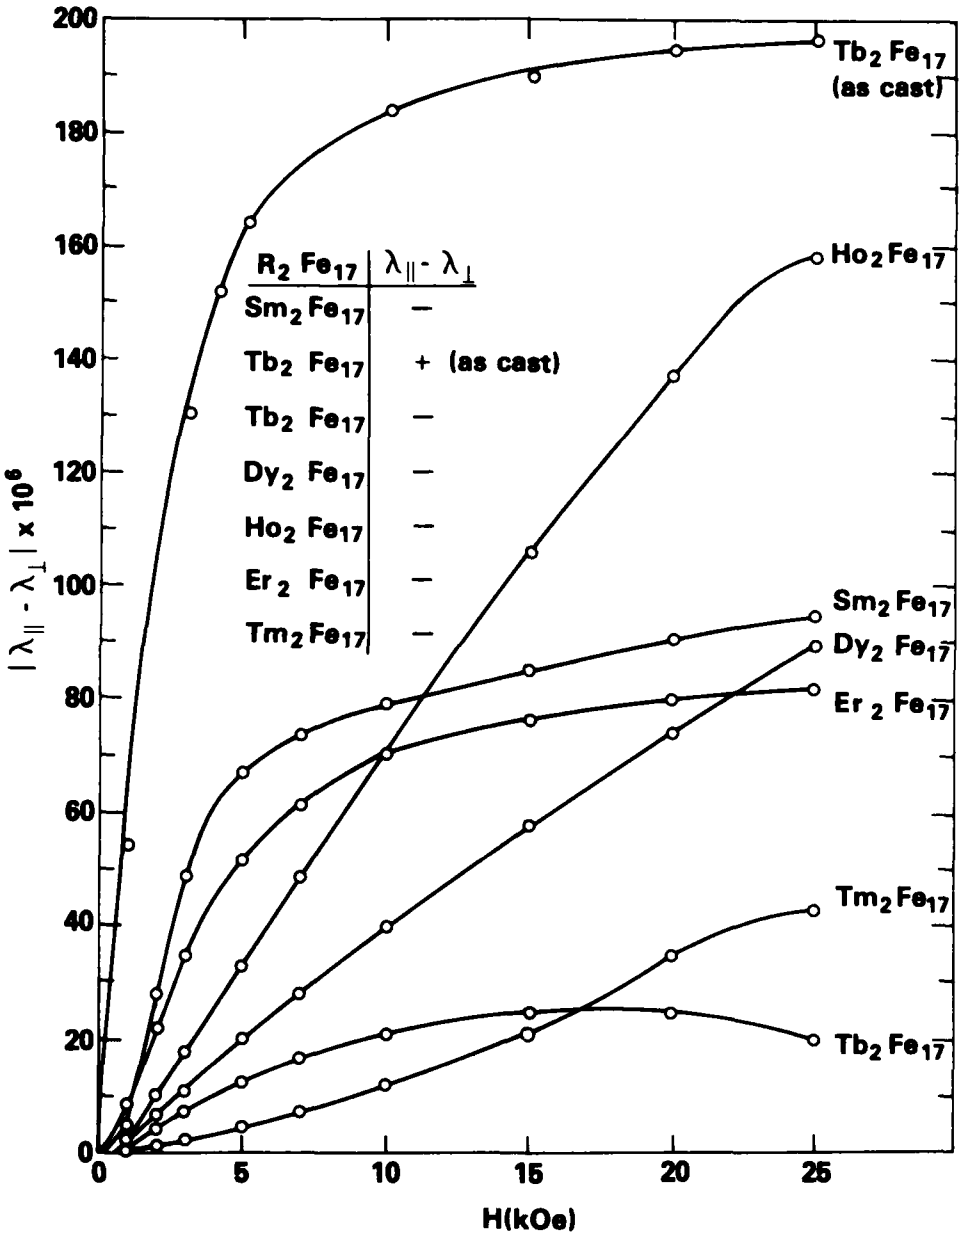

FIGURE 3 ROOM TEMPERATURE MAGNETOSTRICTION AS A FUNCTION OF APPLIED FIELD FOR VARIOUS R_2Fe_{17} COMPOUNDS

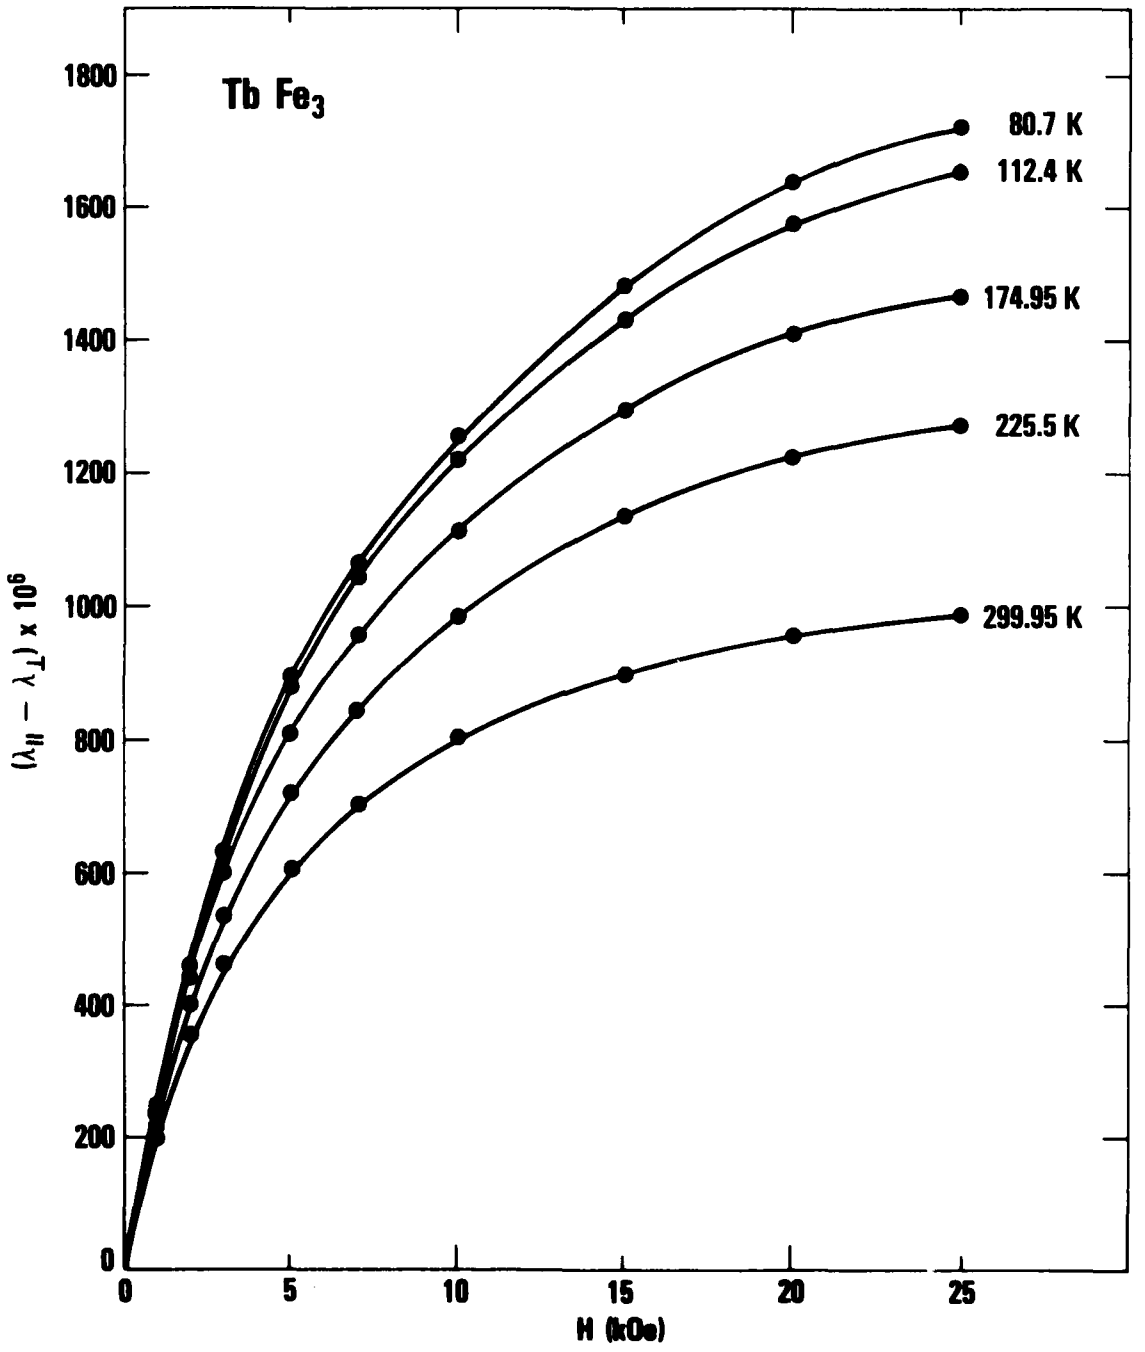

FIGURE 4 MAGNETOSTRICTION AS A FUNCTION OF APPLIED FIELD FOR $TbFe_3$ AT VARIOUS TEMPERATURES

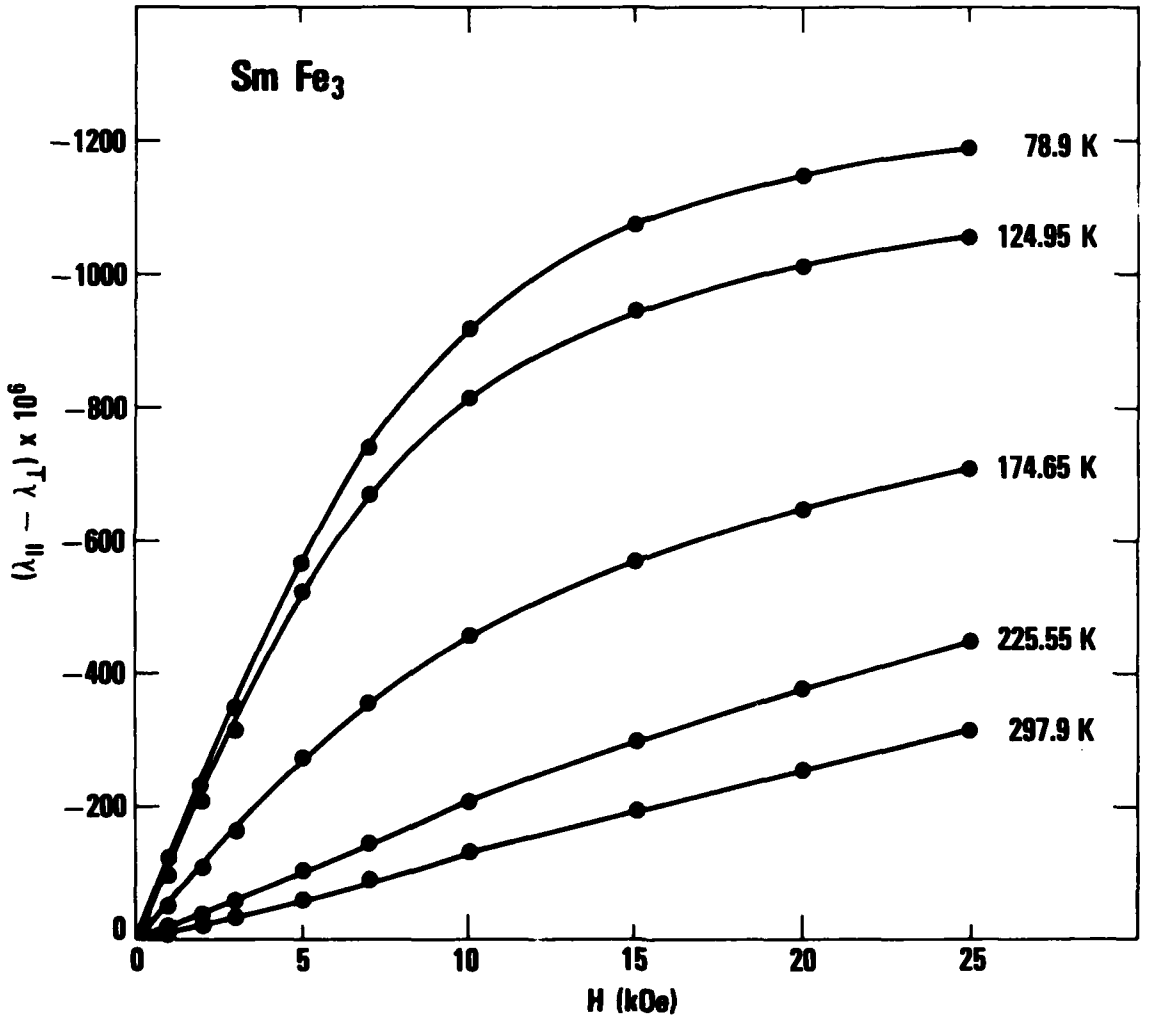

FIGURE 5 MAGNETOSTRICTION AS A FUNCTION OF APPLIED FIELD FOR $SmFe_3$ AT VARIOUS TEMPERATURES

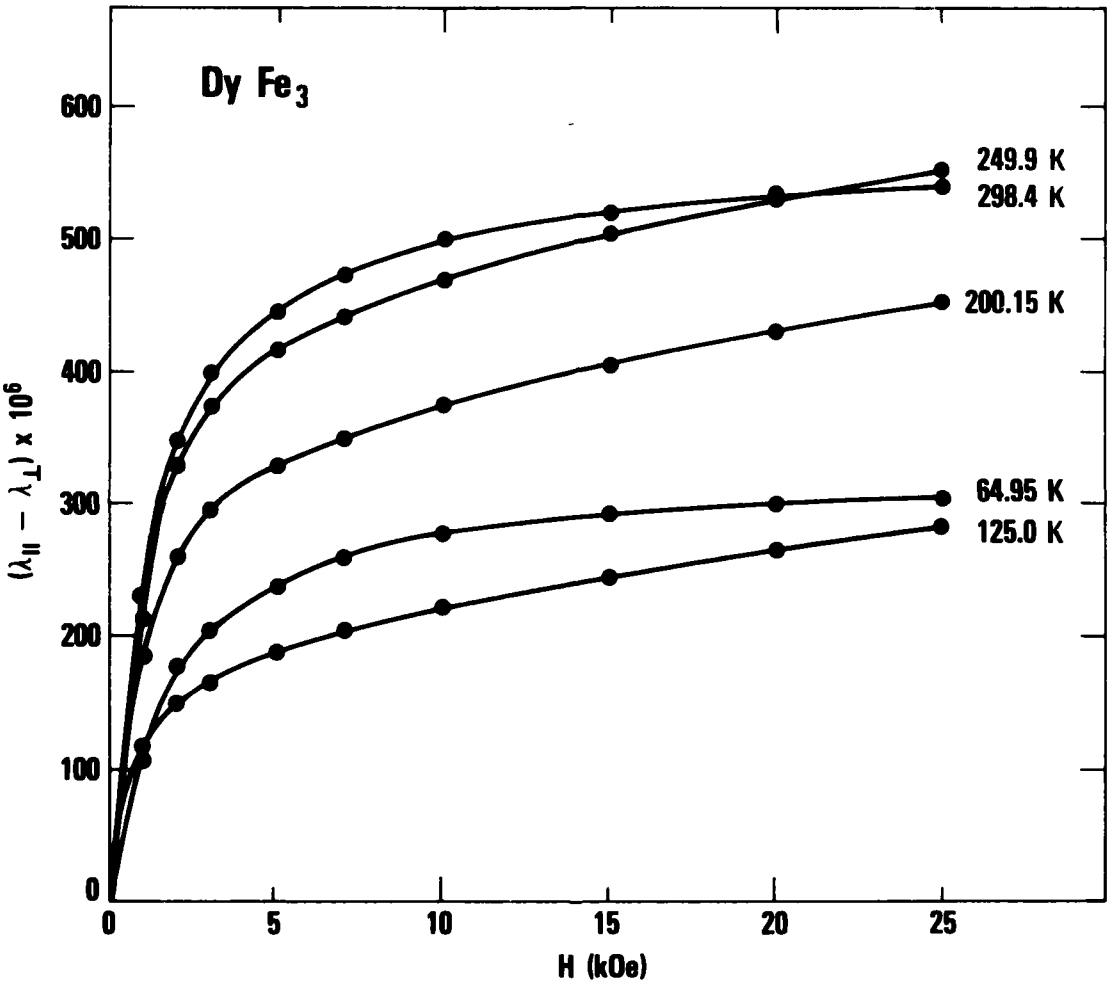

FIGURE 6 MAGNETOSTRICTION AS A FUNCTION OF APPLIED FIELD FOR $DyFe_3$ AT VARIOUS TEMPERATURES

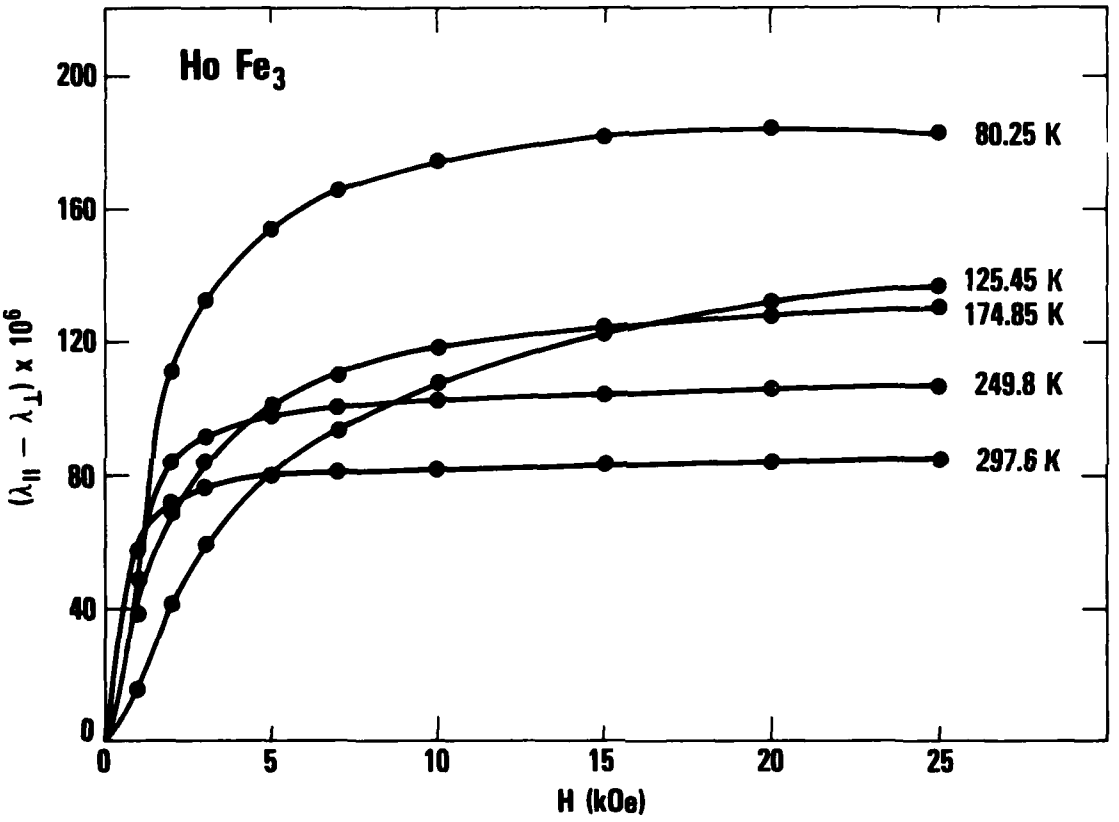

FIGURE 7 MAGNETOSTRICTION AS A FUNCTION OF APPLIED FIELD FOR $HoFe_3$ AT VARIOUS TEMPERATURES

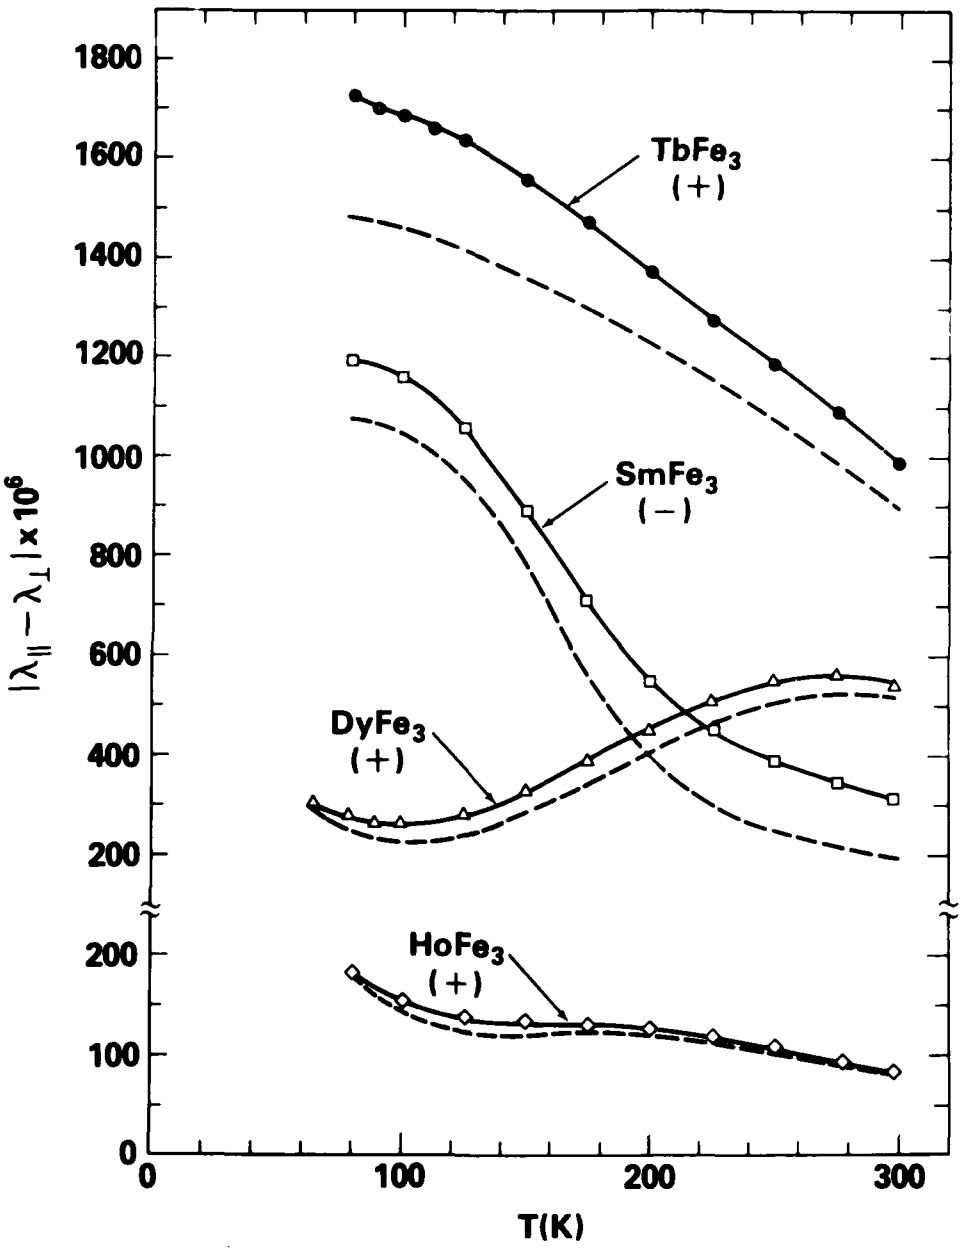

FIGURE 8 TEMPERATURE DEPENDENCE OF THE MAGNETOSTRICTION FOR $TbFe_3$, $SmFe_3$, $DyFe_3$, AND $HoFe_3$ (—— 25kOe, – – -15kOe)

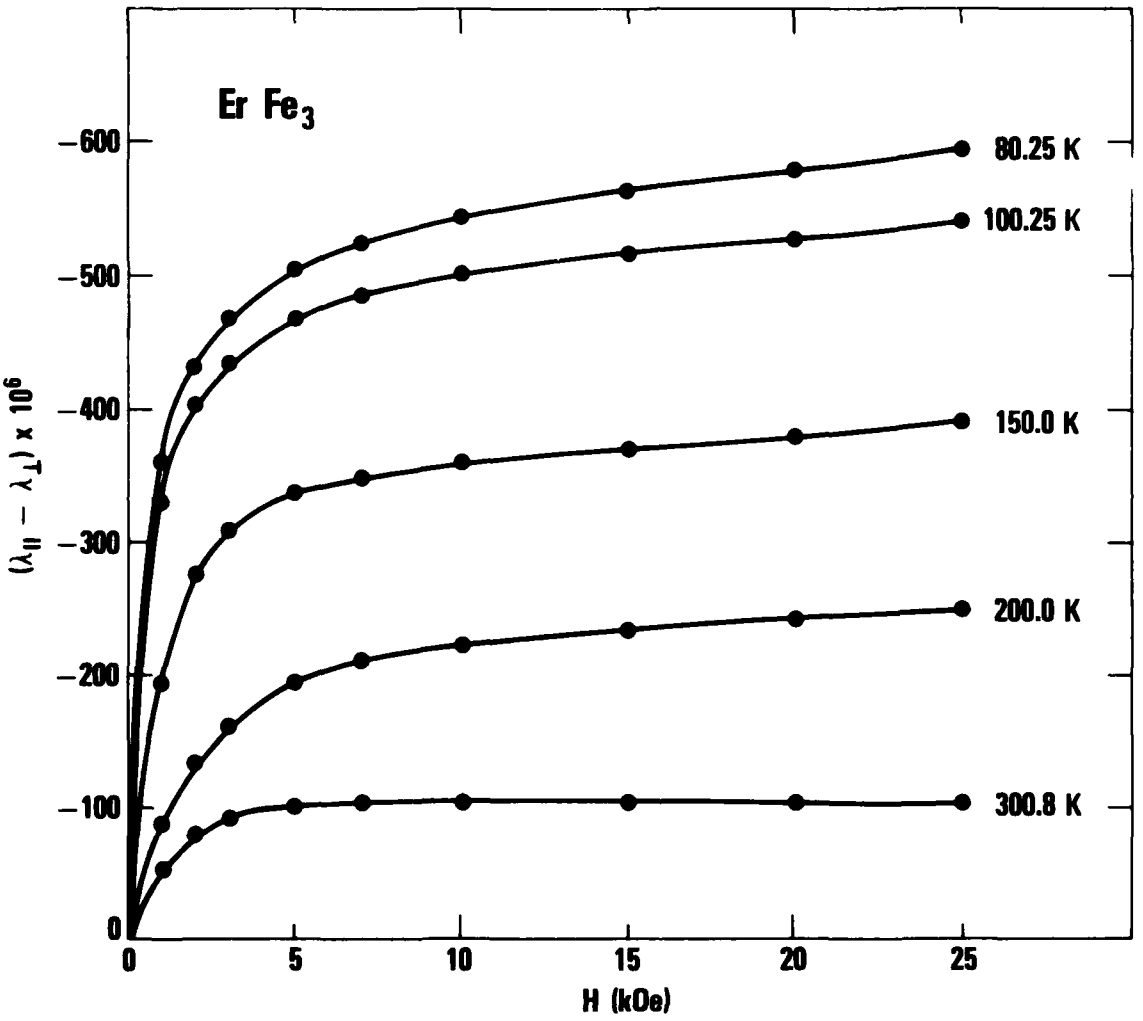

FIGURE 9 MAGNETOSTRICTION AS A FUNCTION OF APPLIED FIELD FOR $ErFe_3$ AT VARIOUS TEMPERATURES

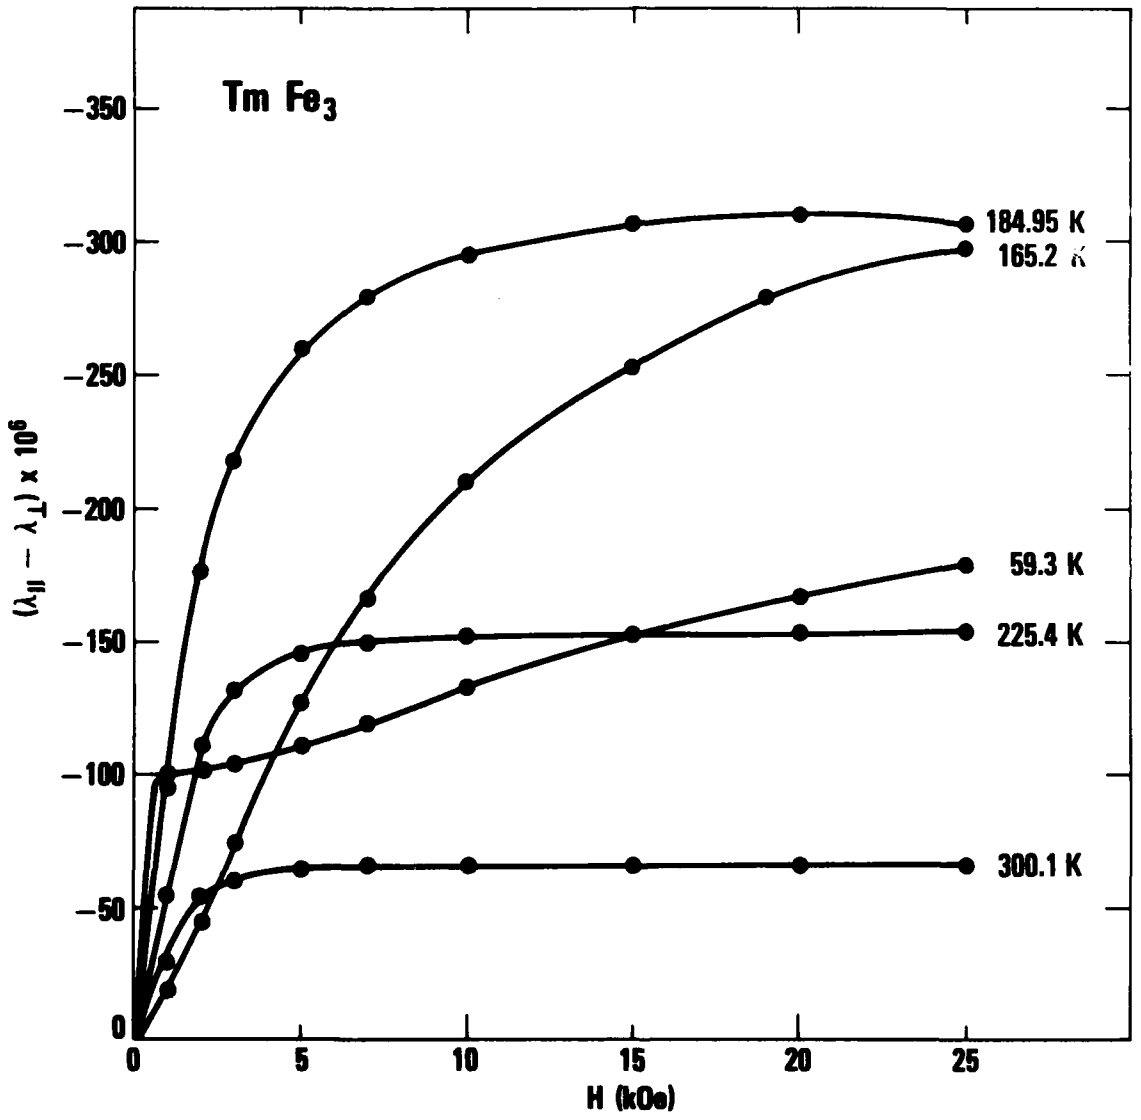

FIGURE 10 MAGNETOSTRICTION AS A FUNCTION OF APPLIED FIELD FOR $TmFe_3$ AT VARIOUS TEMPERATURES

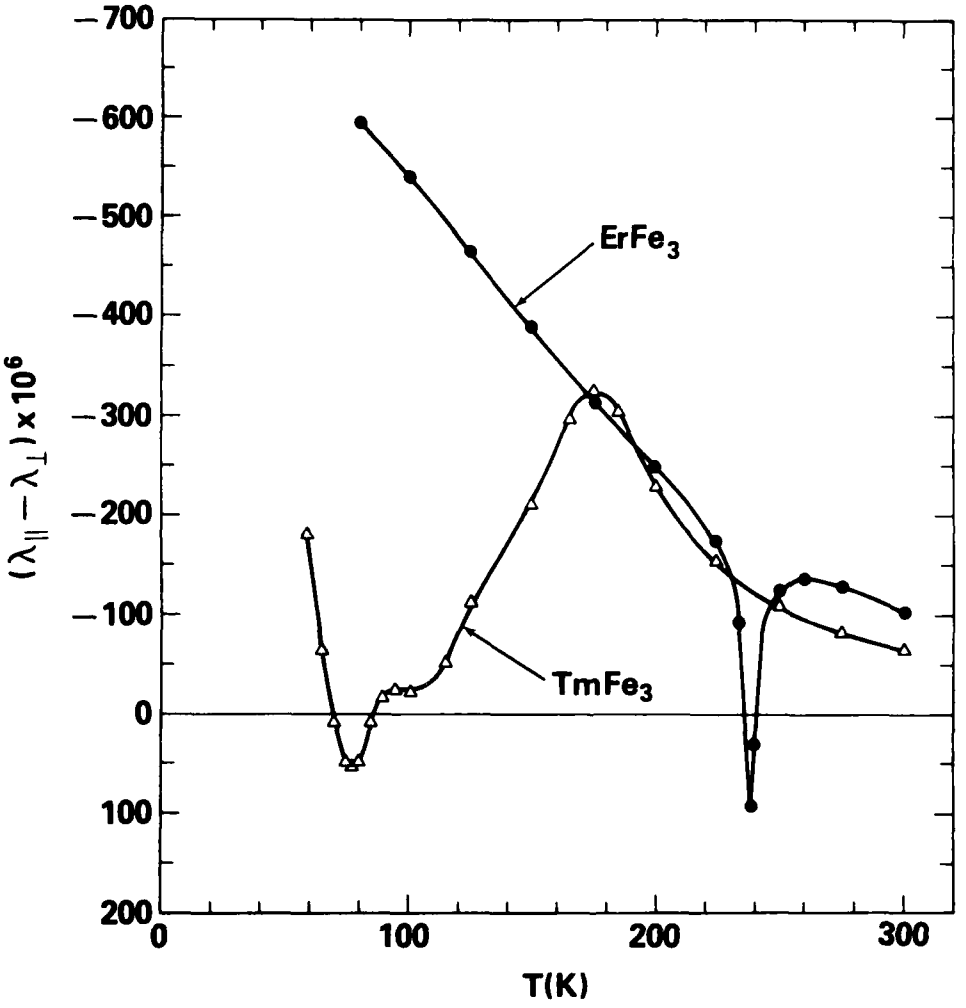

FIGURE 11 TEMPERATURE DEPENDENCE OF THE MAGNETOSTRICTION AT H = 25kOe FOR $ErFe_3$ AND $TmFe_3$

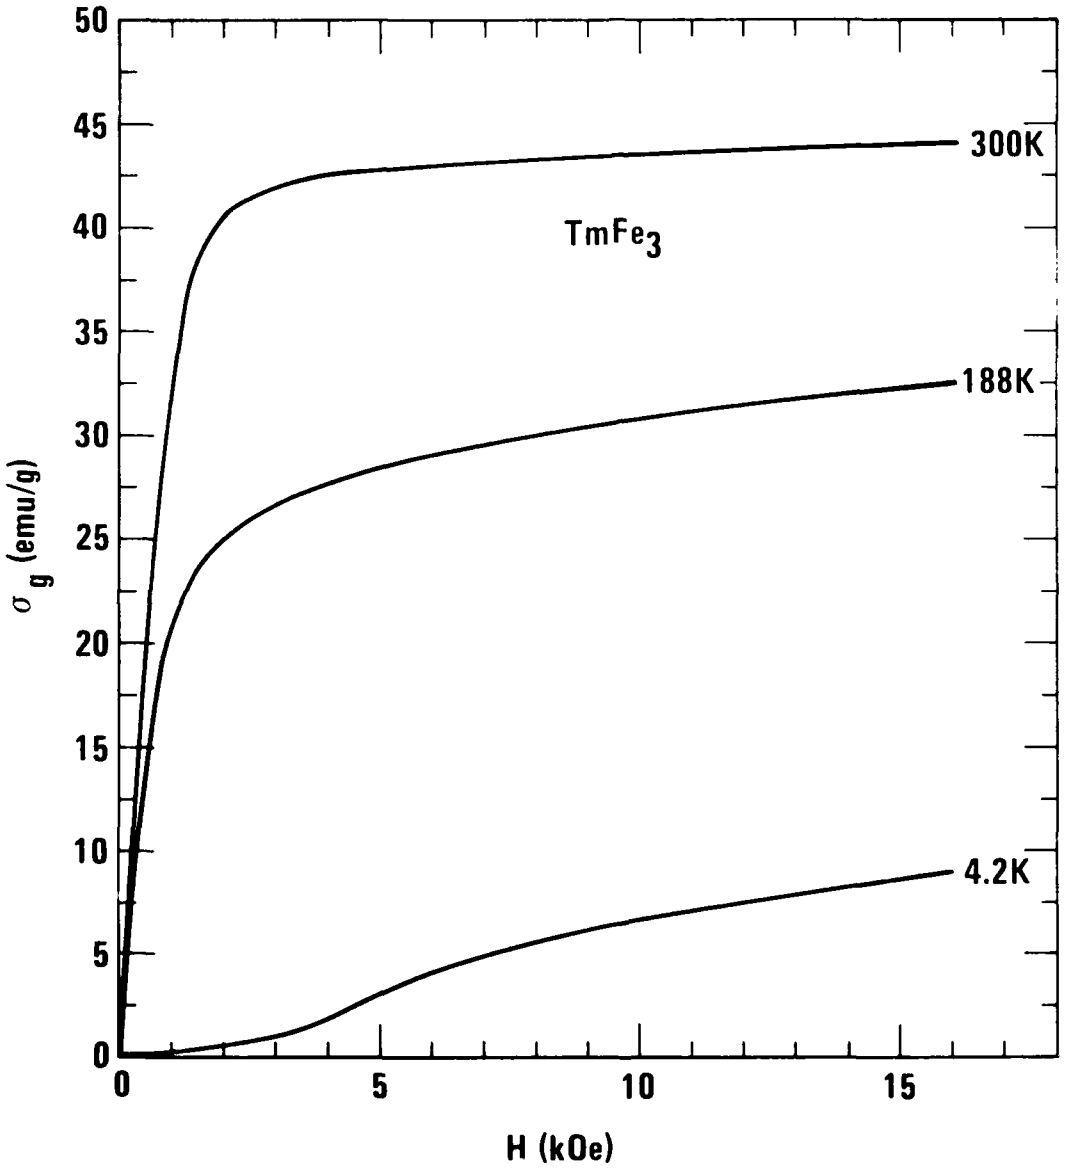

FIGURE 12 MAGNETIZATION AS A FUNCTION OF APPLIED FIELD FOR $TmFe_3$ AT T = 4.2, 188 AND 300K

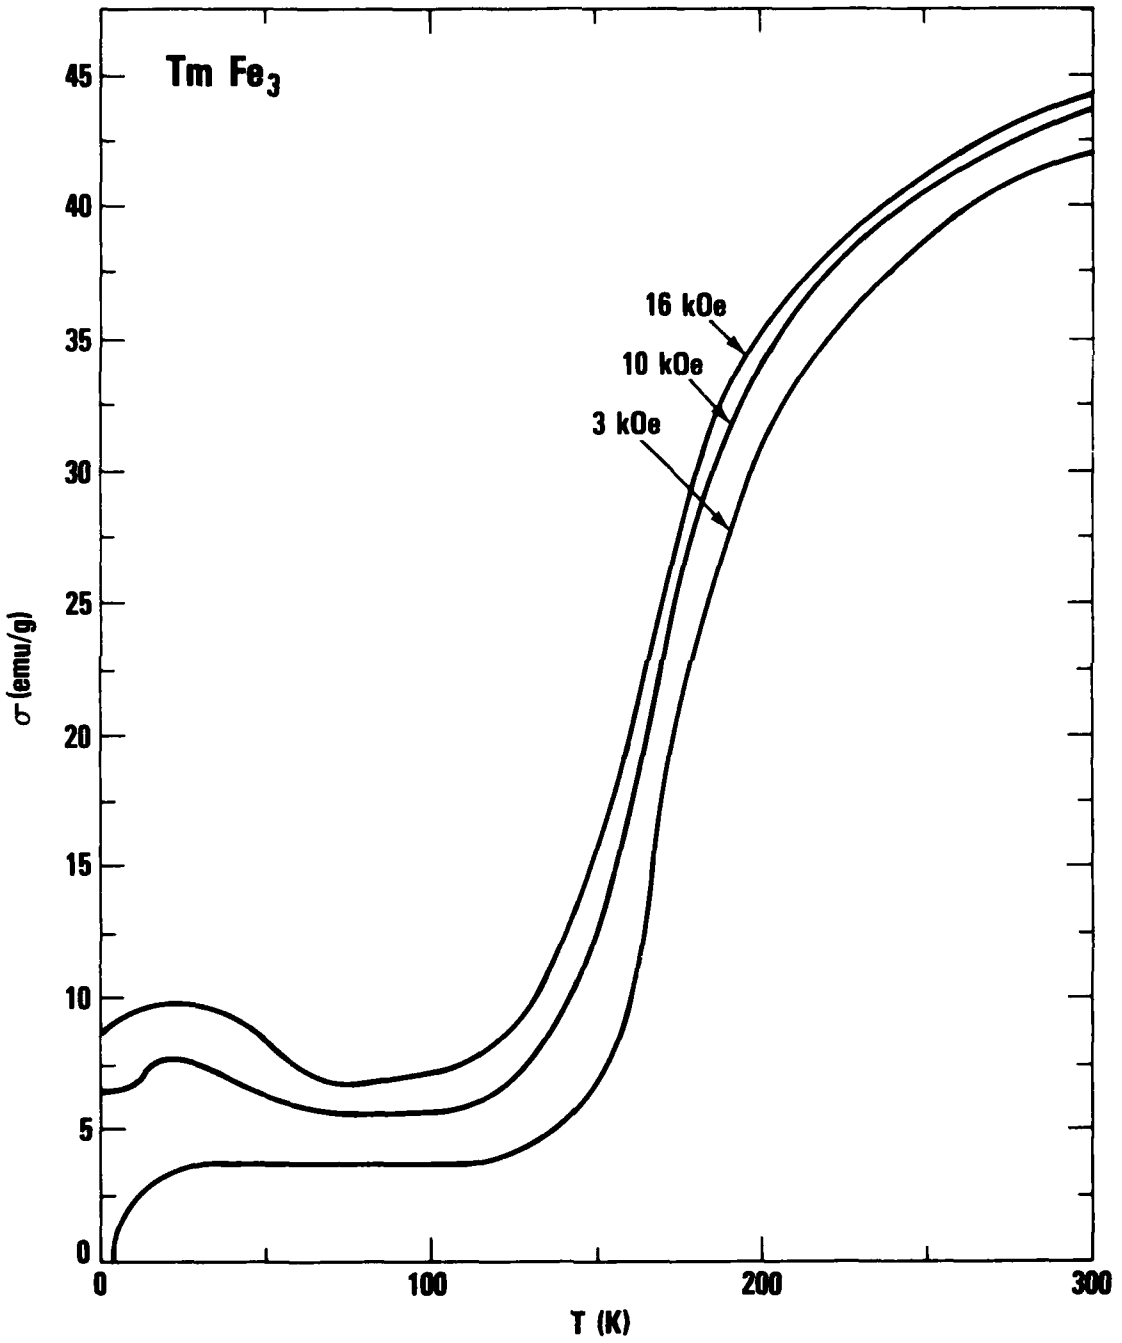

FIGURE 13 TEMPERATURE DEPENDENCE OF THE MAGNETIZATION FOR $TmFe_3$ AT H = 3, 10 AND 16kOe

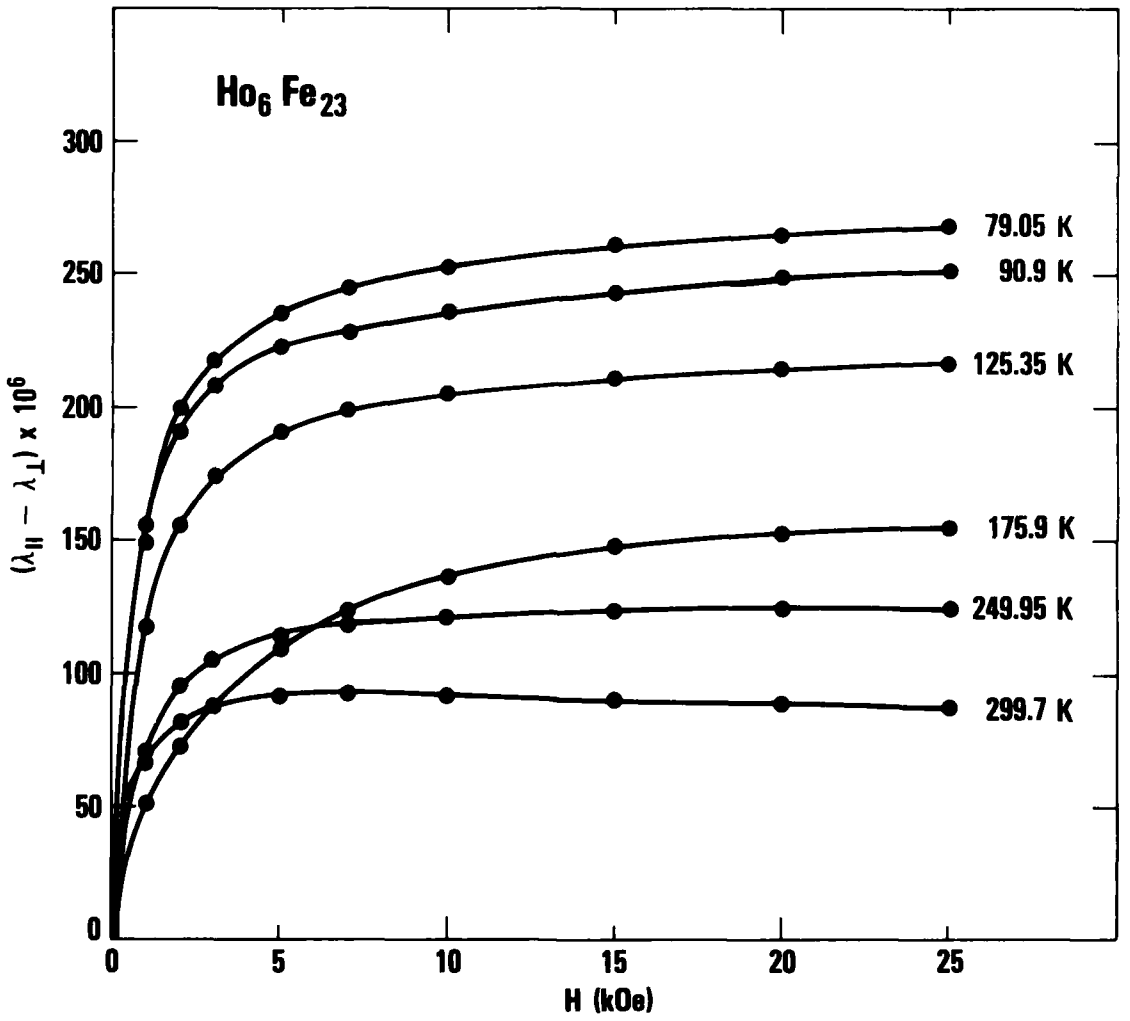

FIGURE 14 MAGNETOSTRICTION AS A FUNCTION OF APPLIED FIELD FOR Ho_6Fe_{23} AT VARIOUS TEMPERATURES

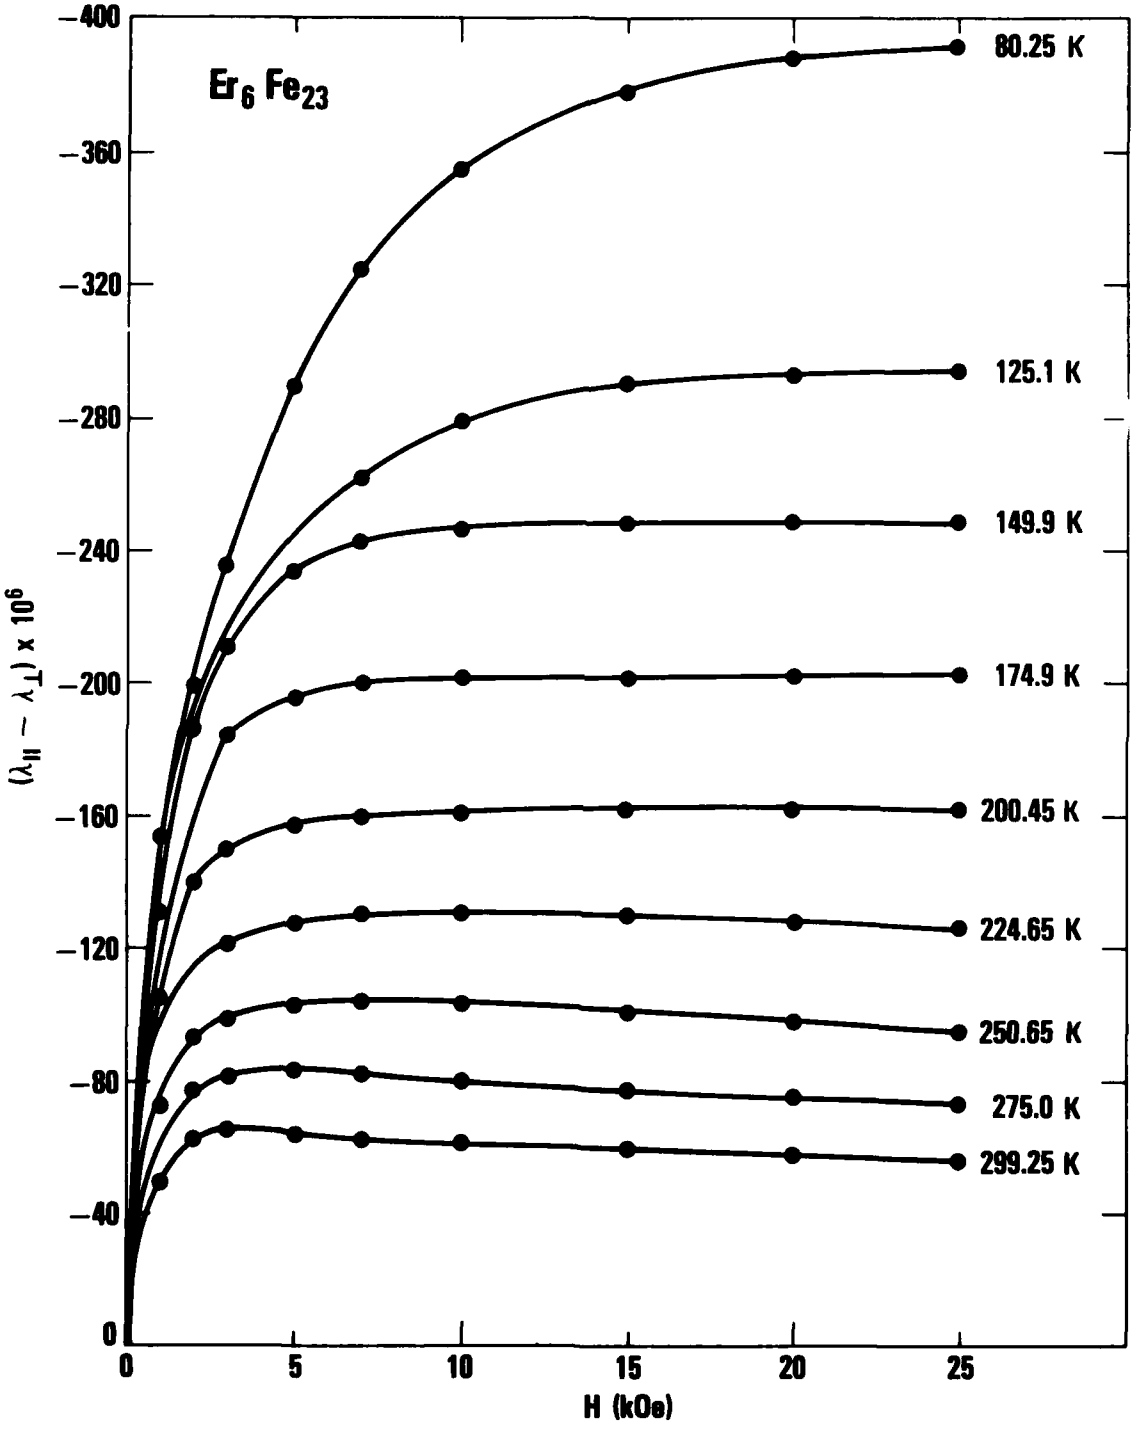

FIGURE 15 MAGNETOSTRICTION AS A FUNCTION OF APPLIED FIELD FOR Er_6Fe_{23} AT VARIOUS TEMPERATURES

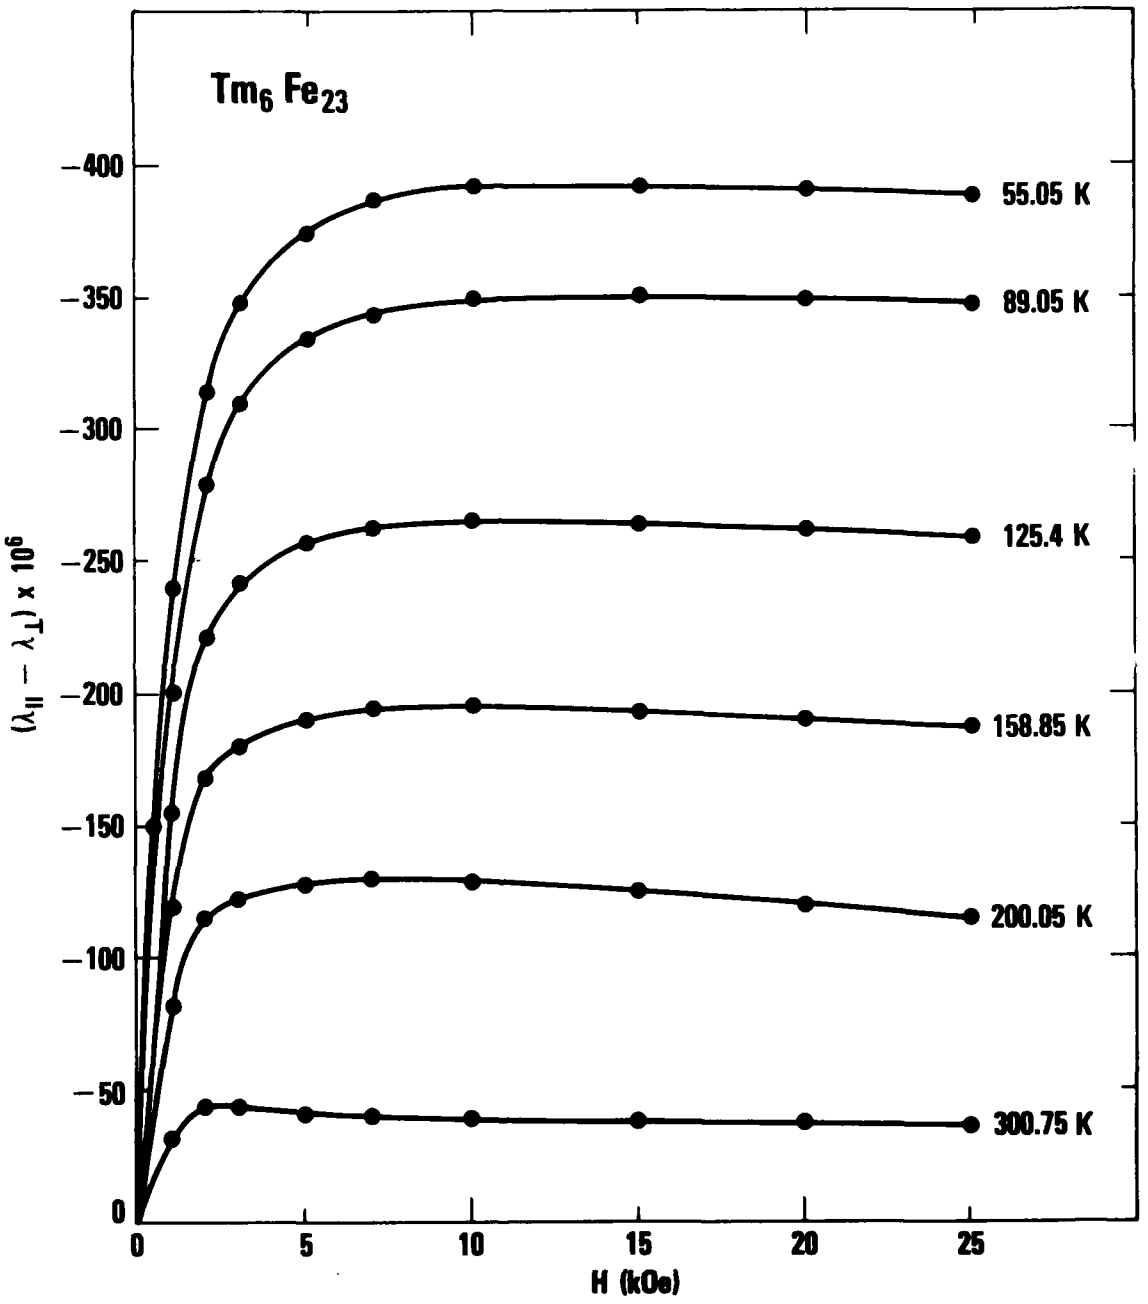

FIGURE 16 MAGNETOSTRICTION AS A FUNCTION OF APPLIED FIELD FOR Tm_6Fe_{23} AT VARIOUS TEMPERATURES

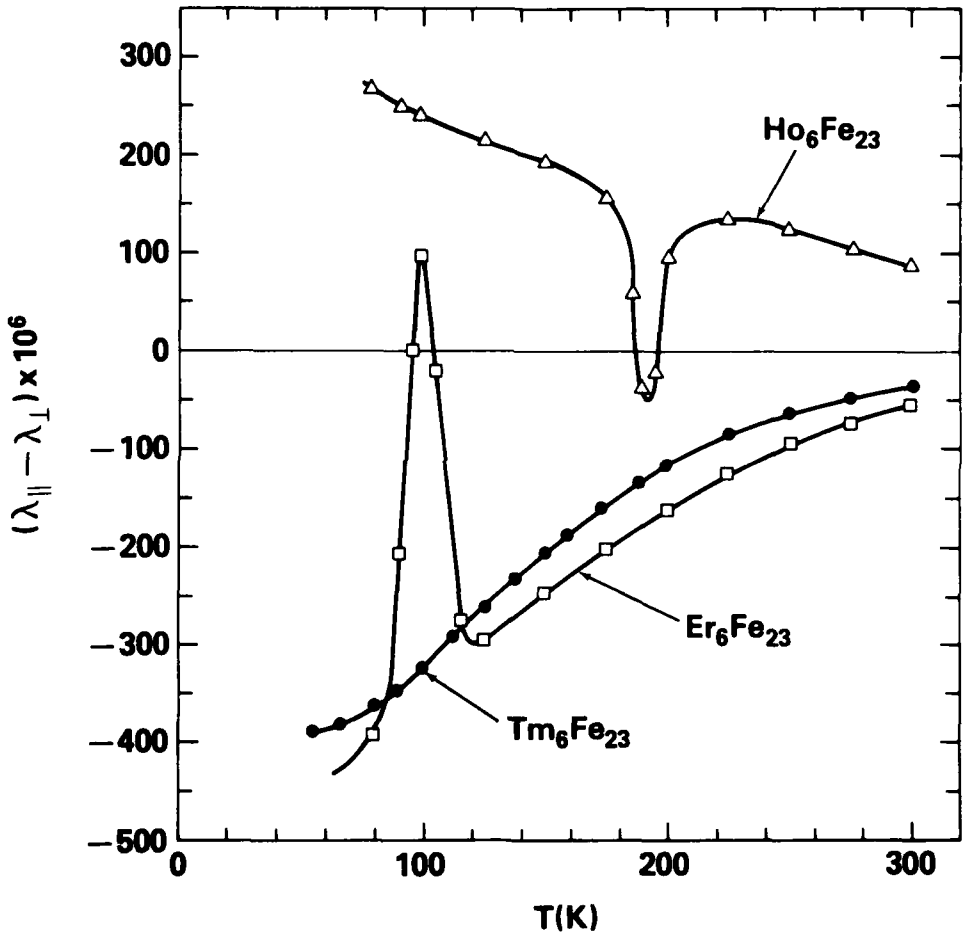

FIGURE 17 TEMPERATURE DEPENDENCE OF THE MAGNETOSTRICTION AT H = 25kOe FOR Ho_6Fe_{23}, Er_6Fe_{23} AND Tm_6Fe_{23}

DISTRIBUTION

	Copies
Naval Air Development Center Code 302 Attn: Mr. F. S. Williams Warminster, PA 18964	1
Naval Air Propulsion Test Center Attn: Library Trenton, NJ 08628	1
Naval Air Systems Command Attn: Code 52031 Code 52032 Washington, DC 20360	1 1
Naval Construction Batallion Attn: Materials Division Civil Engineering Laboratory Port Hueneme, CA 93043	1
Naval Electronics Laboratory Attn: Electron Materials Sciences Division San Diego, CA 92152	1
Naval Facilities Engineering Command Attn: Code 03 Alexandria, VA 22331	1
Naval Missile Center Materials Consultant Code 3312-1 Point Mugu, CA 92041	1
Office of Naval Research Branch Office 1030 East Green Street Pasadena, CA 91106	1
Office of Naval Research San Francisco Area Office One Hallidie Plaza Suite 601 San Francisco, CA 94102	1
Commanding Officer Office of Naval Research Branch Office 536 South Clark Street Chicago, IL 60605	1
Commanding Officer Office of Naval Research Branch Office Building 114, Section D 666 Summer Street Boston, MA 02210	1
Office of Naval Research Department of the Navy 800 N. Quincy Street Attn: Code 471 Code 102 Code 470 Arlington, VA 22217	1 1 1
Naval Postgraduate School Attn: Mechanical Engineering Department Monterey, CA 93940	1
Dr. B. B. Rath Naval Research Laboratory Washington, DC 20375	1
Naval Sea Systems Command Attn: SEA-03B Washington, D. C. 20362	1

	Copies
Naval Research Laboratory	
Attn: Code 6000	1
Code 6100	1
Code 6300	1
Code 6400	1
Code 2627	1
Washington, DC 20375	
Naval Sea System Command	
Attn: Code 035	1
Washington, DC 20362	
Naval Ship Engineering Center	
Department of the Navy	
Attn: Code 6101	1
Washington, DC 20360	
David W. Taylor Naval Ship Research & Development Center	
Materials Department	
Annapolis, MD 21402	1
Naval Undersea Center	
Attn: Library	1
San Diego, CA 92132	
Naval Underwater System Center	
Attn: Library	1
Newport, RI 02840	
Naval Weapons Center	
Attn: Library	1
China Lake, CA 93555	
Scientific Advisor	
Commandant of the Marine Corps	
Attn: Code AX	1
Washington, DC 20380	
Army Materials and Mechanics Research Center	
Attn: Research Programs Office	1
Watertown, MA 02172	
Army Research Office	
Attn: Metallurgy & Ceramics Program	1
P.O. Box 12211	
Triangle Park, NC 27709	
Air Force Materials Laboratory	
Wright-Patterson AFB	
Dayton, OH 45433	1

	Copies
Air Force Office of Scientific Research	
Attn: Chemical Science Directorate	1
Electronics & Solid State Sciences Directorate	1
Bldg. 410	
Bolling Air Force Base	
Washington, DC 20332	
NASA	
Lewis Research Center	
Attn: Library	1
21000 Brookpark Road	
Cleveland, OH 44135	
NASA Headquarters	
Attn: Code RRM	1
Washington, DC 20546	
Defense Documentation Center	
Cameron Station	
Alexandria, VA 22314	12
National Bureau of Standards	
Attn: Metallurgy Division	1
Inorganic Materials Div.	1
Washington, DC 20234	
Argonne National Laboratory	
Metallurgy Division	
P.O. Box 229	
Lemont, IL 60439	1
Defense Metals and Ceramics Information Center	
Battelle Memorial Institute	
505 King Avenue	
Columbus, OH 43201	1
Dr. R. B. Diegle	
Battelle Memorial Institute	
505 King Avenue	
Columbus, Ohio 43201	1
Brookhaven National Laboratory	
Attn: Research Library	1
Technical Information Division	
Upton, Long Island, NY 11973	

	Copies
Professor P. R. Strutt University of Connecticut School of Engineering Department of Metallurgy Storrs, Connecticut 06268	1
Dr. D. G. Ast Cornell University Ithaca, New York 14853	1
Dr. F. E. Luborsky General Electric Company P.O. Box 8 Corporate R&D Schenectady, NY 12301	1
Dr. D. Turnbull Harvard University Department of Engineering & Applied Physics Cambridge, Massachusetts 02139	1
Library Building 50, Rm 134 Lawrence Radiation Laboratory Berkeley, CA 94550	1
Los Alamos Scientific Laboratory Attn: Report Librarian P.O. Box 1663 Los Alamos, NM 87544	1
Professor M. Cohen Massachusetts Institute of Technology Department of Metallurgy Cambridge, Massachusetts 02139	1
Dr. B. C. Giessen Northeastern University 360 Huntington Avenue Boston, Massachusetts 02139	1
Metals and Ceramics Division Oak Ridge National Laboratory P.O. Box X Oak Ridge, TN 37380	1
Dr. J. Mahoney Phrasor Technology 1536 Highland Avenue Duate, California 91010	1

	Copies
Professor William R. Walter Polytechnic Institute of New York Microwave Research Institute Route 110 Farmingdale, NY 11735	1
Professor G. S. Ansell Rensselaer Polytechnic Institute Dept. of Metallurgical Engineering Troy, New York 02181	1
Dr. N. S. Stoloff Rensselaer Polytechnic Institute Troy, New York 12181	1
Dr. E. M. Breinan United Technology Corporation United Technology Research Labs. East Hartford, Connecticut 06108	1
	1
Professor H. G. F. Wilsdorf University of Virginia School of Engineering & Applied Sciences Charlottesville, Virginia 22903	1
Director Applied Physics Laboratory University of Washington 1013 Northeast Forthieth Street Seattle, WA 98105	1

NSWC(W)-5605/1 (Rev. 5-78)

TO AID IN UPDATING THE DISTRIBUTION LIST FOR NAVAL SURFACE WEAPONS CENTER, WHITE OAK TECHNICAL REPORTS PLEASE COMPLETE THE FORM BELOW:

TO ALL HOLDERS OF NSWC/WOL TR 78-88
by R. Abbundi
DO NOT RETURN THIS FORM IF ALL INFORMATION IS CURRENT

A. FACILITY NAME AND ADDRESS *(OLD) (Show Zip Code)*

NEW ADDRESS *(Show Zip Code)*

B. ATTENTION LINE ADDRESSES:

C.

☐ REMOVE THIS FACILITY FROM THE DISTRIBUTION LIST FOR TECHNICAL REPORTS ON THIS SUBJECT.

D.
NUMBER OF COPIES DESIRED _____

END

DATE
FILMED

8-80

DTIC